

Test Report

Number : TWNC0057573401

Applicant: Maymom, LLC
No 20-7 Aly 19 LN333
ChungCheng RD Chunan Mioli County Taiwan

Date : Jan 24, 2017

Sample Description:

One (1) group of submitted samples said to be :

Item Name : (A) Milk bottle center cap, wide
(B) PP Milk bottle 280ml, wide mouth
Batch No. : (A) 11/5/2016
(B) 24/10/2016
Quantity : 7 Pieces
Agent : Maymom
Manufacturer : Maymom
Buyer : Maymom
Country of Origin : Taiwan
Goods Exported to : USA, China, UK, CA.DE
Date Sample Received : Jan 03, 2017
Date Test Started : Jan 03, 2017

Test Conducted:

As requested by the applicant, for details please refer to attached pages.

Conclusion:

Please see page two.

Authorized by:
On Behalf of Intertek Testing Services
Taiwan Limited



Matt Wang
Sr. Manager



Test Report


Number : TWNC0057573401

Conclusion:

<u>Tested Sample</u>	<u>Standard</u>	<u>Result</u>
Tested Components of Submitted Samples	Total Lead (Pb) Content In Non-Surface Coating Materials (Substrate) – As Per U.S. Consumer Product Safety Improvement Act 2008, Title I, Section 101	Pass
	Phthalates Content – As Per U.S. Consumer Product Safety Improvement Act 2008, Title I, Section 108	Pass (#1)
	Test For F.D.A. Regulation On Polypropylene – As Per U.S. 21 CFR F.D.A. Regulation Part 177.1520 Clauses (c)(1.1) And (d)	See Test Conducted
	Bisphenol-A Content – As Per Applicant’s Request	See Test Conducted

Remark: #1 = As requested by the applicant, the test was conducted only on components listed in this report. Other components were not tested.

Authorized by:
On Behalf of Intertek Testing Services
Taiwan Limited

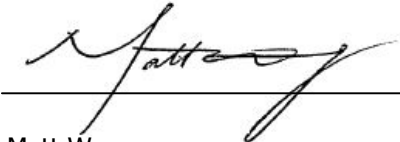

Matt Wang
Sr. Manager





Number : TWNC0057573401

Test Conducted :

1. Total Lead (Pb) Content In Non-Surface Coating Materials (Substrate)

According to CPSIA Test Method: CPSC-CH-E1002-08.3(non-metal) and CPSC-CH-E1001-08.3(metal), by acid digestion and Atomic Absorption Spectrophotometer (AAS) analysis.

<u>Tested Component</u> (1/2)	<u>Result (ppm)</u> ND	<u>Limit (ppm)</u> 100
----------------------------------	---------------------------	---------------------------

Remarks: ppm = Parts per million = mg/kg
ND = Not detected
Detection limit = 20 ppm

2. Phthalates Content

According to CPSIA Test Method: CPSC-CH-C1001-09.3, by solvent extraction and Gas Chromatography-Mass Spectrometer (GC-MS) analysis.

<u>Compound</u>	<u>Result (%)</u> (1/2)	<u>Limit (%)</u>
Diethyl hexyl phthalate (DEHP)	ND	0.1
Dibutyl phthalate (DBP)	ND	0.1
Benzyl butyl phthalate (BBP)	ND	0.1
Di-(iso-nonyl) phthalate (DINP)	ND	0.1
Di-(iso-decyl) phthalate (DIDP)	ND	0.1
Di-(n-octyl) phthalate (DNOP)	ND	0.1

Remarks: % = Percentage based on weight of tested sample
ND = Not detected
Detection limit = 0.005% (for each compound)





Number : TWNC0057573401

Test Conducted :

3. Test For F.D.A. Regulation On Polypropylene

As per the U.S. 21 CFR Food and Drug Administration part 177.1520 clauses (c)(1.1) and (d) with modification on density and melting point.

Test Component: (2)

<u>Test Item</u>	<u>Result</u>	<u>Limit</u>
(A) Density (By Sink-Float Method)	0.896	0.880 – 0.913
(B) Melting Point	150 °C (#2)	160 - 180°C(1.1a) /150 - 180°C(1.1b)
(C) Maximum Extractable Fraction In N-Hexane	2.36 %(W/W)	6.4 %(W/W)
(D) Maximum Extractable Fraction In Xylene	9.74 %(W/W)	9.8 %(W/W)

Remarks : % = Percentage based on the residue by weight
 #2 = The limit of clause 1.1a is for polypropylene consists of basic polymers manufactured by the catalytic polymerization of propylene. And the limit of clause 1.1b is for propylene homopolymer consists of basic polymers manufactured by the catalytic polymerization of propylene with a metallocene catalyst.

4. Bisphenol-A Content

According to specified composite sampling method which was based on the special request of client, solvent extraction method was used and determined by Liquid Chromatography /Tandem Mass Spectrometer (LC-MS-MS).

<u>Tested Component</u>	<u>Result (ppm)</u>
(1/2)	ND

Remarks: ppm = Parts per million = mg/kg
 ND = Not detected
 Detection limit = 0.1 ppm

Test Components:

- (1) White plastic
- (2) Semitransparent plastic





End of Report

Except where explicitly agreed in writing, all work and services performed by Intertek is subject to our standard Terms and Conditions which can be obtained at our website: <http://www.intertek-twn.com/terms/>. Intertek's responsibility and liability are limited to the terms and conditions of the agreement.

This report is made solely on the basis of your instructions and / or information and materials supplied by you and provide no warranty on the tested sample(s) be truly representative of the sample source. The report is not intended to be a recommendation for any particular course of action, you are responsible for acting as you see fit on the basis of the report results. Intertek is under no obligation to refer to or report upon any facts or circumstances which are outside the specific instructions received and accepts no responsibility to any parties whatsoever, following the issue of the report, for any matters arising outside the agreed scope of the works. This report does not discharge or release you from your legal obligations and duties to any other person. You are the only one authorized to permit copying or distribution of this report (and then only in its entirety). Any such third parties to whom this report may be circulated rely on the content of the report solely at their own risk.

